

Scratch and Abrasion Resistant UV Coatings: Various Approaches

*Y. Du, J. Aerykssen, J. Seger, A. Nebioglu
Dymax Corporation
Torrington, CT USA*



Scratch and Abrasion Resistant UV Coatings: Various Approaches

Y. Du, J. Aerykssen, J. Seger, A. Nebioglu

Dymax Corporation

51 Greenwood Rd., Torrington, CT

Abstract

UV-curable nanocomposite coatings of different appearances and properties were prepared and evaluated. Selection of nanoparticles, oligomers, and monomers were made based on market demand of UV-curable urethane acrylate for adhesives and coatings. Targeted improvement areas included antiabrasiveness, tensile strength, hardness, optical clarity, and dimensional stability, while minimizing adhesion loss and elongation. Preparation method of nanoparticle/oligomer/monomer was chosen in consideration of cost effectiveness and, facility accessibility for manufacturing. Functionalized nanoparticles, multifunctional oligomers, and multifunctional monomers were used in developing appropriate products. A number of samples showed significant improvement of antiabrasion, dimension stability, and good adhesion.

Introduction

Polyurethane acrylate oligomers can be polymerized under UV/EB radiation at room temperature in a short period of time. All components in a formulation can be made curable without giving out significant volatile organic components (VOC). Such formulations are plausible candidates for varnishes, adhesives, and coatings when fast curing, temperature sensitive application, and low VOC products are preferred, especially at the time when high output, low environment and regulatory burden, and outstanding performances are a market norm.

Stand-alone oligomeric systems have limitations in mechanical, optical, magnetic, electrical, and/or biological performances, some of them critical for targeted applications. For example, some end users want products with high scratching and abrasion resistances, while others may want transparent products with longevity against weather. Efforts have been made through formulation and embracing new technologies for improvements. In recent years, significant scientific advancements have been made on nanotechnology, the potential of which for many industrial applications have been found in propositions while actual applications are slow due to cost ineffectiveness or facility limitations. In this study, suitability of routine industry instruments and daily QC instruments will be explored for nanoparticle/oligomer development. Different combination of oligomers, nanoparticles, and monomers will be investigated to generate products with noticeable abrasive resistance.

Materials and Methods

Surface modification procedure of particles: active silica based nanoparticle was modified with trimethoxysilane-methacrylate. Nanoparticles were then mixed with oligomers and monomers to obtain samples. Film or test samples were made by UV irradiation on blends following addition of UV initiators. Samples were cured multiple passes at 20 ft/min. In antiscratch test, #0000 steel wool under 8 Oz or 16 Oz hammer head was applied to rub the films being tested for multiple times. The depth of tracks and area of damaged area were then used to characterize the antiabrasion efficacy of samples.

Anti-abrasion test is carried out under Taber model 503 abraser using wheels H-22. Weight loss from 12 stages of 1000 cycle tests were used to rate abrasion resistance. Pick adhesion test was carried out using a utility spatula to pick at the coating. Coatings formed on different substrates with the adhesion samples of interest was picked, and both the degree of difficulty to remove the coating from the substrate and the size of removed coating were used as parameters for adhesion quality. A number between 0 and 5 was assigned to indicate the quality of adhesion, with higher number indicating better quality. Cross-hatch adhesion test was carried out by making a cross-hatch pattern using a Gardco 11 blade 1.5mm crosshatch cutter. After the tape has been applied and pulled off, the cut area is then inspected and rated for adhesion strength. Higher number indicated that more pieces were hatched off by the test, and therefore weaker adhesion. Hardness was tested using a Durometer (Pacific Transducer). Tensile strength and elongation were evaluated using TT-1000 (Chem. Inst.). FTIR (Perkin Elmer Spectrum 100), GPC (Polymer Laboratories PL-GPC-50), viscometer, and DMA (Universal V4.7A TA Instruments) was used to evaluate relevant properties of samples.

Results and Discussion

Nanoparticles, modified or nonmodified, may be able to drastically improve the performance for coating or adhesives.^{1,2,3,4} High functionality oligomers have been selected for its known abrasive resistance. To develop products suitable for market place, not only scientific feasibility should be checked out, technology readiness, such as manufacturing capability and capacity, and cost effectiveness also have to be considered. The design matrix is listed below:

Table 1. Samples investigated in this study.

	Bare Nanoparticle	Functional Nanoparticle
Proadhesion Oligomer, Trifunctional Monomer		F-1
Multifunctional Oligomer, Trifunctional Monomer	BP-2	F-2
Multifunctional Oligomer, Multifunctional Monomer	BP-3	F-3

Dispersion efficacy for nanoparticle/oligomer/monomer blending was monitored by evaluating homogeneity, transparency and viscosity before and after dispersion treatments. Transparency is one shortcoming for particle system. Two product series being investigated in this study, F-2 and F-3, showed no change in visible light absorption, making them eligible for optical applications. Figure 1 is an FTIR chart of F-2 before and after dispersion treatment. Big difference is observed at around the silica absorption peak of $\sim 1100 \text{ cm}^{-1}$ after each treatment, with the most noticeable differences observed after the first and the second treatments.

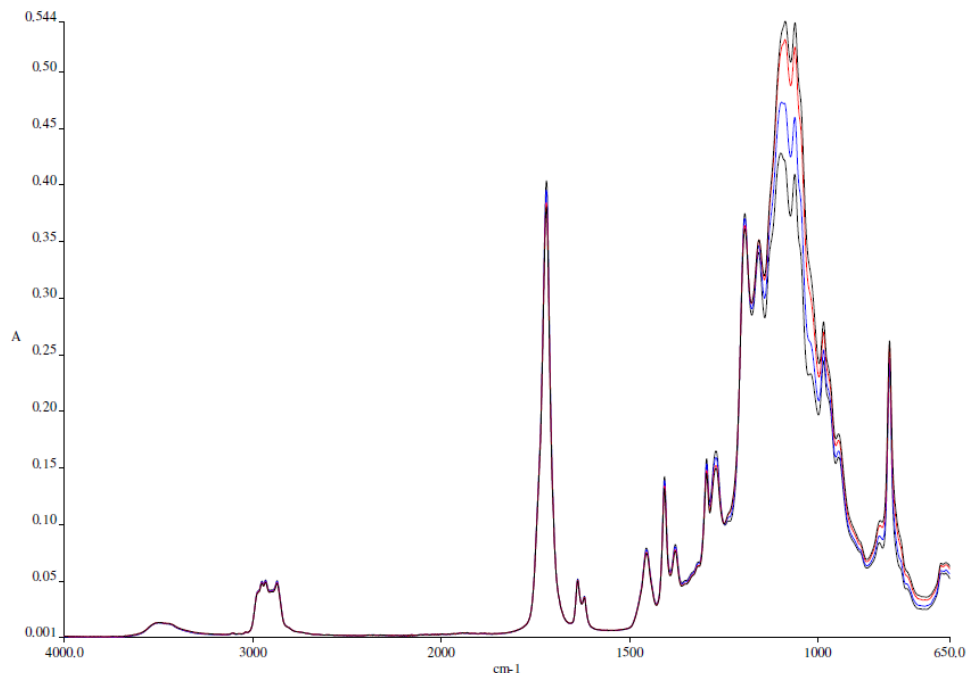


Figure 1. FTIR investigation of F-2. Green – before dispersion treatment. Blue, red and gray – after first, second, and third treatment.

Viscosities also changed after each treatment. Table 2 listed viscosities of F-2 before and after treatments. The morphological change is also visually noticeable, with a more uniform blend obtained through dispersion. Some changed from hazy to transparent. It is believed that dispersion had helped the dissolution of nanoparticles to the oligomeric system, in part by breaking particle aggregates mechanically. Change of viscosities over time was also noticed.

Table 2. Viscosities of nanoparticle/oligomer system at different stages of treatments

	Pre-suspension	Post-suspension
Viscosity day 1 (cP, 25 C, Cap7, 10 rpm)	3125	2156
Viscosity day 30 (cP, 25 C, Cap7, 10 rpm)	2906	2016

DMA analysis of the nanoparticle/oligomer/monomer system was carried out (Figure 2). Over 2 degrees of increase in T_g was observed when 20% nanoparticle was added. To evaluate the change brought by nanoparticles, the apparent cross-linking densities, r , expressed in moles of elastically effective network chains per cubic centimeter of sample, were estimated from the Storage Moduli recorded at T_g+40 C using $r = G'/RT = E'/3RT$, where G' is the shear storage modulus of the cured network at a temperature well above T_g , R is the gas constant and T is the absolute temperature at which the experimental modulus is determined. Cross-linking density with 20% nanoparticles was calculated to be 0.084 moles of elastically effective network chains per cubic centimeter of sample, significantly larger than that of 5% nanoparticles, 0.037 unit. The apparent cross-link density of control sample, which resembles uniformly crosslinked system, is also 0.037 unit.^{5,6}

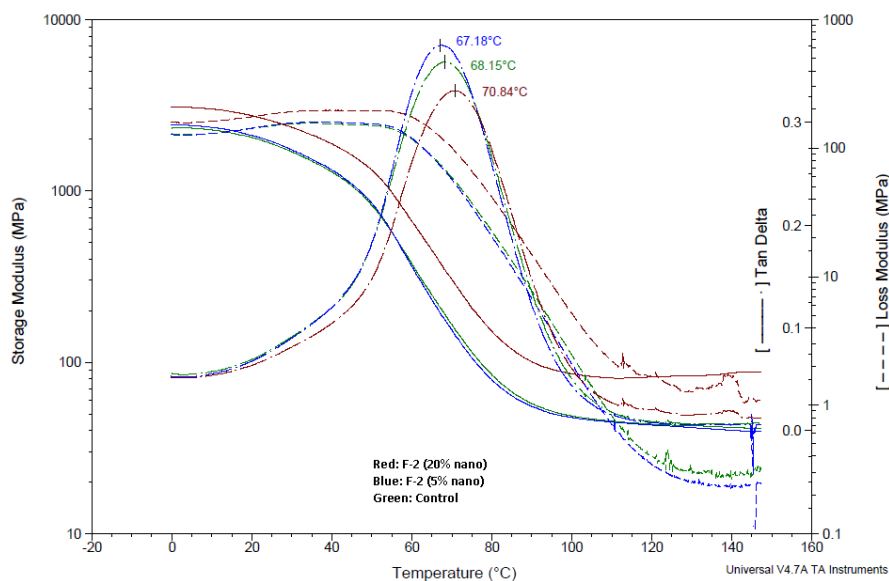


Figure 2. DMA of F-2 with nanoparticle content of 20% (red), 5% (blue), and none (green).

Antiscratch is often essential for coating applications, and was evaluated by steel wool test for samples under study. Most samples included in this report showed good antiscratch properties. Table 3 lists the test matrix and results for two samples. The nanoparticle enforced samples showed outstanding performance against samples without the particles, the control sample.

Table 3. Antiscratch test matrix using #0000 stool wool and test results samples F-2 and BP-2

	Test 1	Test 2	Test 3	Test 4
Wt hammer (Oz)	8	8	8	16
N.o. rubs	3	3	6	6
F-2	Better than BP-2	Better than BP-2	Few faint hazy damage	More damages than test 3
BP-2	Better than Ctrl	10 times better than Ctrl	Few distinct scratches	More damages than test 3
Ctrl			Both faint and distinct damages	Serious damages of both haze and scratches

*2% photoinitiator is used for all samples.

Sample F-2 was tested against wheel abrasion on a Taber Abraser model 503 instrument. Weight losses were monitored as a measure of abrasive resistance during the course of study, approximately 12 stages of 1000 cycles/stage test. Samples with lower nanoparticle contents were also evaluated as a comparison. Figure 3 showed the result. The sample was almost 2 times better than the counterpart control without nanoparticles. Higher nanoparticle content seems to be needed to get noticeable improvements.

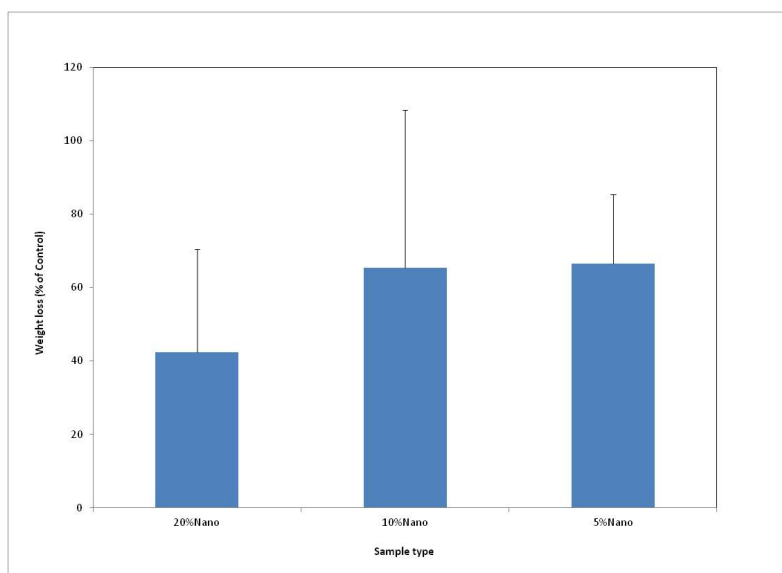


Figure 3. Weight loss of F-2 samples during antiabrasion tests, normalized to the weight loss of control. “20% nano” is a sample with 20% nanoparticles, 40% trifunctional oligomer, and 40% difunctional monomer. “10% nano” is a sample with 10% nanoparticles, 45% trifunctional oligomer, and 45% difunctional monomer. “5% nano” is a sample with 5% nanoparticles, 47.5% trifunctional oligomer, and 47.5% difunctional monomer.

Subsequently, antiabrasion of F-2 was compared against samples in which the composition would be the same as that of F-2 except that nanoparticles were replaced by an equal amount of multifunctional monomer or oligomer. Figure 4 shows the test results of some samples. When nanoparticles were replaced by a multifunctional monomer, e.g. 6-f-m, the abrasion resistance level improved from the control sample where difunctional monomer and trifunctional oligomer were used. When nanoparticles were replaced by a multifunctional oligomer, e.g. six functional oligomer, 6-f-olig, or 15 functional oligomer, 15-f-olig, the abrasion resistance levels were also improved. However, only the sample with nanoparticles showed the most significant improvement in antiabrasion, suggesting the efficacy of nanoparticle enforcement.

Shrinkage due to curing can cause structural variation, dimensional loss, and crack generation, therefore leading to changes of adhesion, scratch resistance, chemical resistance, etc. Minimal shrinkage after curing often is a good indication of a quality product. In this study, shrinkage of the final coating with inclusion of nanoparticles was noticeably less than samples without nanoparticles. It is speculated that the amount of acrylates in a unit volume, as an inverse indicator of “apparent” critical chain length, would decide the shrinkage of samples. The higher the acrylate density, the higher is the shrinkage. It is estimated that by adding 20% nanoparticles to polyurethane acrylates, acrylate density can decrease approximately ~15%, therefore reducing shrinkage extent.

Adhesion is important for adhesives and coatings. Since organic oligomers provide adhesion strength, addition of nanoparticles may affect the adhesion strength of products. Adhesion of samples was evaluated using pick test and cross-hatch test (Table 4). It is found that addition of nanoparticles did not change the adhesion dramatically. More tests are underway to examine the nature of the adhesion and to examine if surface modification of particles changed the interaction pattern of particles with oligomers as well as substrates.

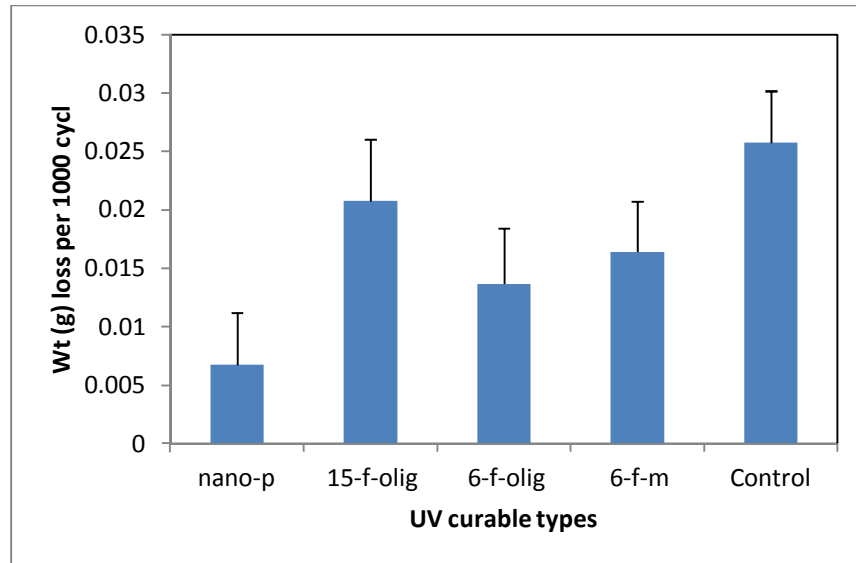


Figure 4. Antiabrasion resistance of samples with different combinations of oligomers, monomers, and nanoparticles. “nano-p” is a sample with 20% nanoparticles, 40% trifunctional oligomer, and 40% difunctional monomer. “15-f-oligo” is a sample with 20% 15 functional oligomer, 40% trifunctional oligomer, and 40% difunctional monomer. “6-f-oligo” is a sample with 20% 6 functional oligomer, 40% trifunctional oligomer, and 40% difunctional monomer. “6-f-m” is a sample with 20% 6 functional monomer, 40% trifunctional oligomer, and 40% difunctional monomer. “Control” is a sample with 50% trifunctional oligomer, and 50% difunctional monomer.

In pick test, higher number indicated stronger force being needed to pick removed coating from substrate. In cross-hatch test, higher number indicated larger number of coating spots being hatched off from substrate. The samples tested did not show significant changes with or without nanoparticles, indicating that oligomers and monomers may have “wetted” nanoparticles well and dominated the interaction with substrates.

Table 4. Pick test and cross-hatch test of nanoparticle/oligomer/monomer systems.

	Pick		Cross-hatch	
	F-2	Control	F-2	Control
PolyCarbonate	2	2	100	100
PolyAcrylate	2	3	100	92
ABS	4	3	100	96
HDPE	1	0	84	85
Steel	0	2	100	97
Aluminum	1	2	100	100
Stainless S	1	2	100	89

In summary, all tests so far indicated that some nanoparticle enforced systems in our study improved antiabrasion, antiscratch, and shrink resistance while maintaining good adhesion and optical transparency.

Conclusions

Polyurethane acrylate based UV-curable nanocomposite coatings were prepared and evaluated. Both surface modified and nonmodified nanoparticles were investigated. Oligomers and monomers with different functionalities were selected to generate nanocomposite samples. Selections were based on the consideration of niche market demand of products with projected specifications, company product portfolio, and facility requirements. Targeted improvement areas included antiabrasiveness, tensile strength, hardness, optical clarity, and dimensional stability, while minimizing adhesion loss and elongation. Results indicated that some systems in this report showed outstanding scratch resistance, antiabrasive resistance, reduced shrinkage loss, and optical clarity. Adhesion did not change significantly on substrates Polycarbonate, Polyacrylate, ABS, HDPE, Steel, Aluminum, Stainless Steel, and Glass.

References

1. Ahmet Nebioglu, *Network Formation and Thermomechanical Properties of Photo-curing Hybrid Coatings*. Ph.D thesis University of Akron, May 2006
2. Technology Partnership, Energetics, Incorporated, *Chemical Industry R&D Roadmap for Nanomaterials By Design: From Fundamentals to Function*, December 2003. <http://www.chemicalvision2020.org/nanomaterialsroadmap.html>
3. Willems & van den Wildenberg (W&W), *Roadmap Report on Nanoparticles. The 6th Framework Programme (FP6) of the European Commission* November 2005
4. Krotine, S. Ramsey, *UV-Curable Coatings with Nanotechnology-enabled Barrier Properties*, Radtech UV & EB 2008 Conference, May 7, 2008.
5. L. W. Hill, *Paint and Coating Testing Manual*, J. V. Koleske Ed., Fourteenth Ed. Gardner-Sward Handbook, ASTM, Philadelphia, PA, 1995; Ch. 46, p. 534
6. L. E. Nielsen, *J. Macromol. Sci-Revs. Macromol. Chem.*, C3, 69, 1969



© 2012 Dymax Corporation. All rights reserved. All trademarks in this guide, except where noted, are the property of, or used under license by Dymax Corporation, U.S.A.

The data contained in this bulletin is of a general nature and is based on laboratory test conditions. Dymax does not warrant the data contained in this bulletin. Any warranty applicable to the product, its application and use is strictly limited to that contained in Dymax's standard Conditions of Sale. Dymax does not assume responsibility for test or performance results obtained by users. It is the user's responsibility to determine the suitability for the product application and purposes and the suitability for use in the user's intended manufacturing apparatus and methods. The user should adopt such precautions and use guidelines as may be reasonably advisable or necessary for the protection of property and persons. Nothing in this bulletin shall act as a representation that the product use or application will not infringe a patent owned by someone other than Dymax or act as a grant of license under any Dymax Corporation Patent. Dymax recommends that each user adequately test its proposed use and application before actual repetitive use, using the data contained in this bulletin as a general guide.

OCWP001 5/2012

Dymax Corporation
860.482.1010
info@dymax.com
www.dymax.com

Dymax Oligomers & Coatings
860.626.7006
oligomers&coatings@dymax.com
www.dymax-oc.com

Dymax Europe GmbH
+49 (0) 611.962.7900
info_de@dymax.com
www.dymax.de

Dymax UV Adhesives & Equipment (Shenzhen) Co Ltd
+86.755.83485759
dymaxasia@dymax.com
www.dymax.com.cn

Dymax Asia (Hong Kong) Ltd
+852.2460.7038
dymaxasia@dymax.com
www.dymax.com.cn

Dymax Korea LLC
82.2.784.3434
info@dymax.kr
www.dymax.co.kr